

This is a postprint version of the following published document:

Loayza, A., Cabanelas, J. C., González, M. G. & Baselga, J. (2015). Critical examination of chemically modified hybrid thermosets: Synthesis, characterization and mechanical behavior in the plateau regime of polyaminosiloxane-nitrile-DGEBA. *Polymer*, 69, pp. 178-185.

DOI: [10.1016/j.polymer.2015.05.054](https://doi.org/10.1016/j.polymer.2015.05.054)

© Elsevier, 2015



This work is licensed under a Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International License.

Critical examination of chemically modified hybrid thermosets: Synthesis, characterization and mechanical behavior in the plateau regime of polyaminosiloxane-nitrile-DGEBA

Artemia Loayza, Juan C. Cabanelas, María González, Juan Baselga*

Department of Materials Science and Engineering and Chemical Engineering, Universidad Carlos III de Madrid, Av. Universidad 30, 28911 Leganés, Madrid, Spain

* Corresponding author. mail address: jbaselga@ing.uc3m.es (J. Baselga).

ABSTRACT

Poly(3-aminopropylmethylsiloxane) has been modified with acrylonitrile via aza Michael addition and a broad range of modified oligomers have been prepared with CN:NH₂ ratio ranging between 0.1 and 1. NMR and FTIR analysis reveals that acrylonitrile modification proceeds without formation of tertiary amines. Modified oligomers have been characterized by DSC and analysis of T_g reveals that the adducts are self-associated probably due to weak hydrogen bonding and dipole interactions. The modified oligomers with a modification degree higher than 0.4 were miscible with DGEBA. The low and high temperature relaxations of the cured thermosets have been measured by DMTA. In addition to the commonly observed β_2 relaxation, a new β_1 process linked by an isosbestic point to β_2 has been found. β_1 is attributed to an extended segment comprising the pendant propionitrile group as well as the ami-nopropyl segment that connects tertiary amines to the polysiloxane backbone. Elastic modulus as well as the α relaxation can be tuned from high T_g and high rubbery modulus to low T_g and high damping thermosets changing the nitrile content. The experimental network structure obtained from elastic measurements and the T_g were related through well established structure-property relations.

KEYWORDS

Epoxy resins
Hybrid thermoset
Polysiloxane

1. Introduction

The structure and properties of epoxy/siloxane reactive blends is currently an open question in the field of advanced thermosetting materials. Both components are immiscible and phase segregation limits the morphology and phase composition, size and distribution. Several efforts to improve the compatibility by introducing reactive groups in the silicon-based component have been compiled in a recent review [1]. Common approaches include the functionalization of the inorganic siloxane backbone with reactive functional end-groups [2] (epoxy, amine, acrylate or isocyanate), the synthesis of siloxane block copolymers with a resin compatible segment [3] or the introduction of pendant reactive groups [4]. This last solution was adopted by our group in earlier reports on the synthesis of poly(3-aminopropylmethyl siloxane) (PAMS) and its curing with DGEBA based epoxy resins [5,6].

Crosslinking agents for epoxy resins based on polyfunctional aminosiloxanes render very interesting polymer-polymer hybrid systems in which structure changes dramatically with both chemical conversion [5,6] and polymerization protocol [7]. They belong to the class of hybrid thermosetting blends and present a number of distinctive features. Contrary to conventional thermosets, a phase separated system consisting of PAMS spherical domains surrounded by the continuous epoxy matrix is formed upon mixing both reactants. In spite of their thermodynamic incompatibility, both components begin to react and, depending on the specific epoxy precursor and curing protocol, homogeneous (at the micron scale) or partially homogeneous thermosetting polymers are formed [7,8]. Another distinctive characteristic is related with their modification. They can be modified by physical mixing with conventional toughening agents, such as butadiene homo- and copolymers yielding a fine morphology [8]; but if a small amount of PMMA is used, a polymer with an extremely high affinity for the epoxy precursor, an *aphron*-like morphology is obtained in which the reactant mixture self organizes into polyhedral aphyrons excluding the PMMA towards the interphase [9].

However, the most interesting feature is probably concerned with their high functionality which, at the same time, increases the Young's modulus in the rubbery state, increases hydrophobicity [10] and switches gelation towards lower conversion fixing the final morphology well before limiting conversion. This high functionality can be tuned reacting some of the pendant amino groups with molecules that may impart specific properties while the remaining provide enough crosslinking density to give high performance thermosets. An earlier successful attempt was done reacting some amino groups with 2,3-Epoxypropyl phenyl ether [11] aiming to delay gel conversion and to increase miscibility with DGEBA. However, the T_g and viscosity of the modified oligomers notably increased due to the bulkiness of the pendant group limiting the suitability of this approach.

In this work, we present a new alternative for modification of PAMS using the well-known aza-Michael addition reaction of aliphatic primary amines to acrylonitrile [12], which, as we will show, proceeds extremely well in this particular case yielding modified PAMS oligomers with highly polar cyano groups. Firstly we will present the synthesis and characterization of these adducts demonstrating the absence of double additions, i.e. the modified oligomers contain a controlled ratio between primary and secondary amines. Next, the adducts will be used to prepare a broad range of organo-inorganic thermosets differing in the amount of nitrile groups, i.e., different crosslinking densities, finding that for CN:NH₂ ratios higher than 0.4, homogeneous systems at the micron scale are formed. The paper then focuses on the analysis and critical interpretation of the low and high temperature relaxations and in their elastic behavior. The high T relaxations will be explained using the concentration of elastically active network chains obtained from elastic measurements.

2. Experimental part

2.1. Materials

Diglycidyl ether of bisphenol-A (DGEBA, $M = 377 \text{ g mol}^{-1}$, $n = 0.14$) and acrylonitrile (AN, 99% purity) were purchased from Sigma–Aldrich. 3-aminopropylmethyldiethoxysilane (APDES) was purchased from ABCR GmbH (97% purity) and used without further purification.

2.2. Synthesis and characterization of poly(3-aminopropylmethylsiloxane) precursor

Poly(3-aminopropylmethylsiloxane) (PAMS) was synthesized from APDES by hydrolysis and condensation in aqueous solution according to methods already reported [5,6,13]. Molar mass and cyclic content were measured by MALDI-TOFF spectrometry (4700 Proteomics Analyzer, Applied Biosystems) with external calibration. Spectra were taken in reflector mode focusing on 1500 μm . Sample was dissolved in dichloromethane (1 mg mL⁻¹). Matrix solution was prepared with 2,5-dihydroxybenzoic acid (10 mg mL⁻¹) in ethanol: dichloromethane (25:75). Sample and matrix solutions were mixed (1:10 ratio) and 0.5 μL aliquot was deposited onto the MALDI sample holder. Results show that PAMS consists of a mixture of linear and cyclic oligomers; cyclics amount 40.6% in number with number and weight average molar masses of $M_n(C) = 744 \text{ g mol}^{-1}$ and $M_w(C) = 926 \text{ g mol}^{-1}$. The number and weight average molar masses of the linear fraction are $M_n(L) = 1250 \text{ g mol}^{-1}$ and $M_w(L) = 1508 \text{ g mol}^{-1}$. The average molar masses of the sample are $M_n = 1036 \text{ g mol}^{-1}$ and $M_w = 1343 \text{ g mol}^{-1}$. The number and weight average polymerization degrees are $x_n = 8.74$, $x_w = 11.35$. Consequently, the average monomer molecular weight is $118.52 \text{ g mol}^{-1}$.

2.3. Synthesis and characterization of PAMS-acrylonitrile adducts

PAMS-acrylonitrile adducts were synthesized via aza-Michael addition reaction (Scheme 1). Nine adducts were prepared with varying CN:NH₂ ratio from 10% to 100%. Samples were designed as Ax, where x is the nominal percentage of AN (Table S1 Supplementary material). In a typical experiment, adequate amounts of AN were added dropwise over 4 g of pure PAMS at room temperature (23 °C) in a 25 mL double necked round flask continuously purged with a small N₂ stream and with slight agitation. Temperature was measured all along the reaction (Fig. S1 Supplementary material); although reaction was completed in less than 20 min, agitation and N₂ stream were maintained for 2 h and then the reaction mixture was vacuum distilled to remove AN traces and stored at -4 °C in vacuum. Adducts characterization was done by FTIR (Perkin Elmer, GX2000) in both the medium (4000–400 cm⁻¹) and near ranges (7500–4000 cm⁻¹) (four scans, 4 cm⁻¹), and by ¹H NMR (AVANCE DPX-300). ¹H NMR (CDCl₃, 298 K, 300 MHz), δ (ppm): C1 (0.47, m; 2H), C2 (1.44, m; 2H), C3 (2.61, m; 2H), C4 (2.44, t(br); 2H), C5 (2.83, t; 2H).

2.4. Curing of adducts with DGEBA

For DMTA measurements, the following method was used to prepare specimens. Stoichiometric amounts of DGEBA and adducts were thoroughly mixed, vacuum degassed and introduced in a steel mold which was previously treated with a releasing agent (Fre-kote®). The mold was designed to obtain 25 × 10 × 2 mm³ specimens. Mold was heated up to 120 °C in an oven for 2 h followed by a postcuring treatment at 140 °C for 30 min. This curing protocol ensured full conversion as it was verified by the absence of residual heat in DSC and by the absence of residual epoxy and amine bands by FTIR. Samples were designated as ThAx.


Cured specimens were characterized by dynamic mechanical thermal analysis (DMTA, TA Instruments, Q 800, bending mode, 1, 10 and 30 Hz, 2 °C min⁻¹). The high temperature relaxation, T_α , was measured at the maximum in $\tan \delta$ at 1 Hz. Moduli data in the elastomeric state were obtained at $T = T_\alpha + 50 \text{ K}$.

Density measurements of the cured specimens were carried out in an He pycnometer (Micromeritics, AccPyc 1330) at 35.1 °C with a typical standard deviation of 2 kg m⁻³. For calculation of the concentration of elastically active chains from modulus values at $T_g + 50\text{K}$, density data were corrected at that temperature using typical data for the linear thermal expansion coefficient, α_L , below (50 10⁻⁶ K⁻¹) and above (170 10⁻⁶ K⁻¹) glass transition temperature for epoxy resins cured with amines [14], through the use of the following relation $\rho(T) = \rho(T_0)/[1 + 3\alpha_L \Delta T]$. This correction decreased density data in 3–4%, one order of magnitude higher than typical standard deviation of the measurement.

3. Results and discussion

3.1. Synthesis and characterization of the adducts

The aza-Michael reaction is a well-known method to conjugate amines to α,β unsaturated nitriles [15]. It usually requires basic conditions [16], such as the medium provided by the pure PAMS used here, and high conversions are usually achieved at moderate temperatures. The method used here does not use any solvent since PAMS is a low viscosity liquid in which AN readily dissolves, and we have found that the reaction is highly exothermic reaching almost completeness in a short period of time, typically less than 20 min (see Fig. S1 Supplementary material). The two main parameters of the synthesized adducts that are needed to characterize the starting monomers for the network formation with epoxy resin are the

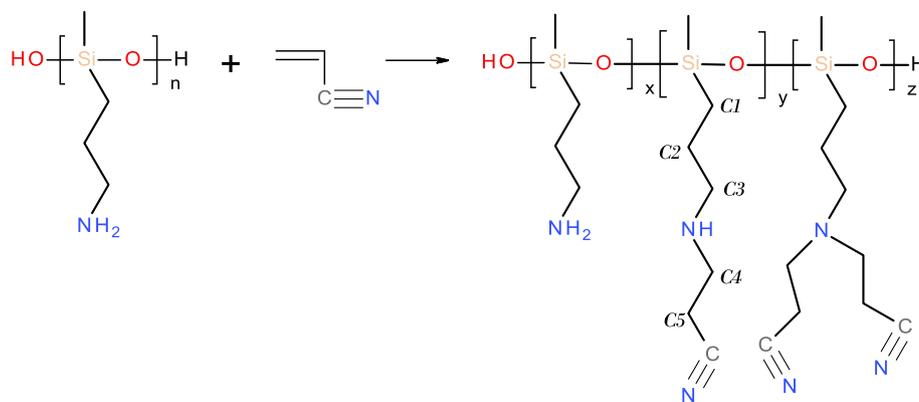

Scheme 1. Random modification of PAMS via aza-Michael addition of AN. C1–C5 are ^1H NMR assignments. x , y and z represent the amount of primary amines, single Michael addition and double Michael addition respectively.

amount of AN effectively coupled, which determines the functionality of the adduct, and the presence of double additions (segment z in Scheme 1), which would create tertiary amines introducing dangling ends in the network.

^1H NMR was used to measure the extent of the coupling reaction. Fig. 1 shows the ^1H NMR spectra for PAMS and some selected adducts; the peak labels are explained in Scheme 1.

Amine signals broaden, decrease in intensity and position of signals is moved to a lower value of the chemical shift as the extent of coupling increases. They are generally strongly affected by hydrogen bonding, concentration or even protonation being thus not adequate for quantification. The signals of protons C4 and C5 from the AN moiety appear around the signal of PAMS C3 protons. At all AN contents, C4 peak overlaps the C3 PAMS peak being not adequate for integration. Peak C5 (AN) and C1 and C2 (both from PAMS) are well resolved at low AN contents, but as AN content increases above 50%, C5 tail overlaps with C3 tail being extremely difficult to separate the signals of both protons. Since our main interest is to ensure that addition reaction has reached total conversion, we have used two integration methods that overestimate (absolute integration) and underestimate (base line corrected integration) the signals of protons and calculated an average composition. Results are shown in Fig. 2 where the ratio AN: NH_2 obtained from NMR integration is plotted against the feed molar ratio.

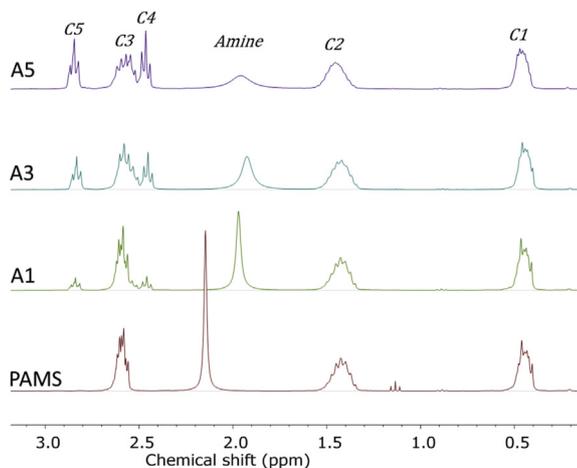


Fig. 1. ^1H NMR spectra of PAMS and some selected adducts. Peak labels are indicated in Scheme 1.

It is worth noting the extremely good correlation between both magnitudes which confirms that aza-Michael addition reached 100% conversion under our experimental conditions.

^1H NMR does not provide information about possible double additions, so we have also analyzed the FTIR spectra of all the samples. Fig. S2 (Supplementary material) shows the spectra in the mid-infrared range and Fig. S3a (Supplementary material) shows the spectra in the near range. In the mid-range, it can be clearly observed the gradual disappearance of the primary amine bending band (1600 cm^{-1}) and the substitution of the two stretching bands at $3400\text{--}3300\text{ cm}^{-1}$ by a single band (3400 cm^{-1}), which is characteristic of secondary amines [17]; in the near-range, the band appearing at $\sim 6500\text{ cm}^{-1}$, gradually changes its shape from 6534 cm^{-1} , an overtone of primary amines, to 6479 cm^{-1} , characteristic of secondary amines. These observations clearly suggest that single aza-Michael addition on PAMS primary amines has taken place in all cases, that is to say, no tertiary amines should be expected. For quantitative purposes we have analyzed the primary amine broad combination band centered at 4937 cm^{-1} which is easy to integrate (Fig. S3). However, this band shows a non-assigned high energy shoulder that gradually disappears with AN

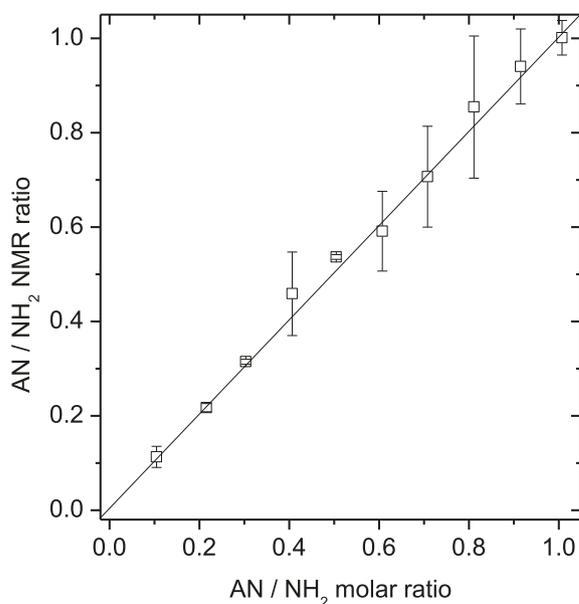


Fig. 2. AN/ NH_2 ratio from NMR integration against the molar ratio used in the feed. Line is the diagonal.

content. For a proper integration, only the low energy half portion of the band has been considered as shown in Fig S3b.

Results of the FTnIR integration are shown in the form of percentage of reacted primary amine as a function of initial concentration of AN in Fig. 3. Depending on the relative reactivity of primary and secondary amines, R_{21} , the extent of double Michael addition can be important especially at high AN contents. Although it is generally assumed that the reactivity of aliphatic secondary amines is higher than primary amines because they are more nucleophilic [12], it has been also reported that due to electronic or steric hindrance secondary amines may present low reactivity [18]. In our case, the nitrile acceptor group may inductively deactivate the secondary amine reducing its reactivity against Michael addition.

To ascertain whether single or double addition has taken place, we have simulated two realistic cases: i) secondary amine has very low reactivity, and ii) reactivity of primary and secondary amines is the same. In case i) the percentage of reacted amine is directly given by the AN:NH₂ ratio. For case ii) the percentage of reacted primary amine can be easily calculated from simple probabilistic arguments [19] as $100 \times [1 - (1-r)^2]$, where $r = 2[NH_2]_0/[AN]_0$. Both simulations are jointly represented in Fig. 3 where it can be clearly observed that experimental data coincide extremely well with case i). Thus, double addition is negligible under our experimental conditions and, consequently, the synthesized adducts do not contain any appreciable amount of tertiary amines, i.e. $z \approx 0$ in Scheme 1.

The molar mass and composition of the modified oligomers, as obtained from MALDI, NMR and FTnIR, are summarized in Table S1 (Supplementary material).

Glass transition temperatures of the adducts were measured by DSC and the results are presented in Fig. 4. The adducts were considered as copolymers of the two monomers shown in Scheme 1; monomer 1 containing the -NH₂ functionality and monomer 2 containing the -CN functional group.

Glass transition temperatures of the random copolymers present positive deviations of the Flory-Fox behavior suggesting

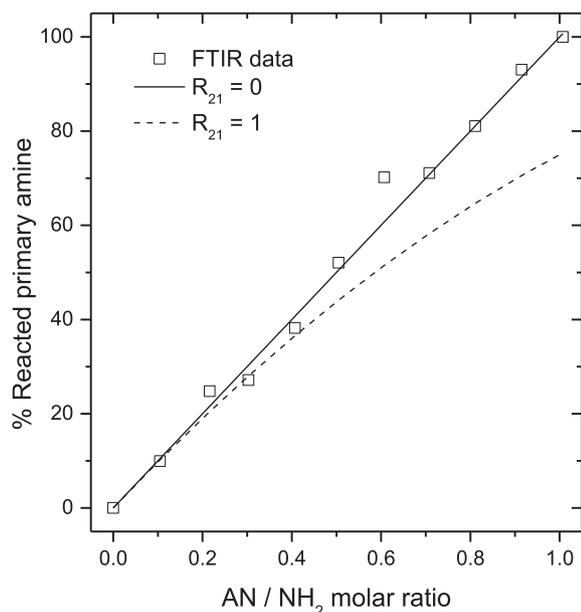


Fig. 3. Percentage of reacted primary amine as obtained from FTnIR as a function of the initial AN/NH₂ molar ratio in the feed. Continuous and dash dotted lines represent theoretical predictions assuming secondary to primary amine reactivity, R_{21} , equal to 0 or 1 respectively.

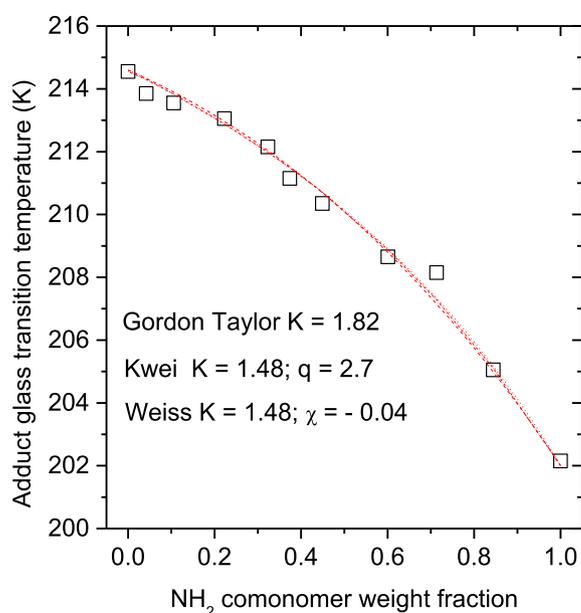


Fig. 4. Glass transition temperature of PAMS and adducts as a function of the weight fraction of NH₂ comonomer in the copolymer. Data correspond to fitting parameters. Lines are best fits to Gordon Taylor, Kwei and Weiss models.

relatively strong intermolecular interactions. Data could be fitted to the Gordon Taylor equation leaving the constant K as a fitting parameter [20] giving a value of the fitting constant $K_0 = 1.82$; values of $K_0 > 1$ are common in systems where there are attractive interactions [21]. However, since K_0 has unclear physical meaning we have fitted the data to other models that consider attractive interactions such as the Kwei equation [22] or the Weiss model [23]. In these models, the parameter K is defined as in the Couchman's model [24] $K_C = \Delta C_{p1}/\Delta C_{p2}$, i.e., the ratio between the heat capacity changes at the glass transition temperature of both polymers (PAMS and A10). The measured value of K_C was 1.48 and it was used as a fixed constant. Kwei model yields a value of the q constant of 2.7; Weiss model yields a slightly negative value of the Flory-Huggins interaction parameter. However, since T_g values vary in a narrow temperature range (14 K) both models predict very similar trends and differences are lower than experimental uncertainty in the T_g determination. It can be therefore concluded that adducts are self-associated probably due to weak hydrogen bonding between -NH₂, -NHR and -CN groups as well as by dipole-dipole interactions between -CN groups.

3.2. Relaxations of the cured networks

Stoichiometric mixtures of the well characterized adducts with DGEBA were cured as explained in the experimental part and the low and high temperature relaxations were analyzed by DMTA. Fig. 5a–b shows the storage and loss moduli and the $\tan \delta$ variation of the cured specimens in the temperature range 25–200 °C; $\tan \delta$ variation in the low temperature range is presented in Fig. 6.

3.2.1. Low temperature relaxations

Low temperature relaxations were analyzed in terms of the temperature variation of the loss tangent (Fig. 6), activation energies and peak temperatures (Fig. 7). PAMS/DGEBA network presents a broad relaxation (β_2) centered at about -50 °C (Fig. 5c) which is attributed to a complex set of motions that involve both the hydroxypropylether group O-CH₂-CHOH-CH₂ and the DGEBA ring flips, as it is commonly found in epoxy resins [25]. The

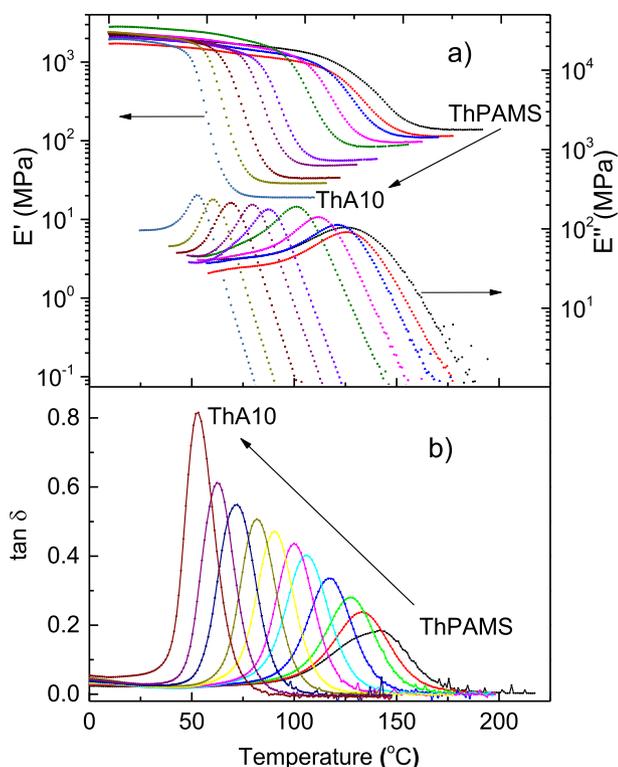


Fig. 5. Storage and loss moduli (a) and loss tangent at 1 Hz (b) for ThPAMS and the adducts cured with DGEBA, ThAx.

activation energy calculated from Arrhenius plots of $\tan \delta$ at 1, 10 and 30 Hz (not shown) is $E_a(\beta_2) = 65 \pm 4 \text{ kJ mol}^{-1}$ (see Fig. 7) which is coincident with reported data for highly crosslinked epoxy systems [25].

On addition of acrylonitrile loss tangent decreases and β_2 peak clearly shifts to lower temperatures (Figs. 6 and 7). This result indicates that the amount of hydroxypropylether groups decreases becoming progressively more mobile; this is in accordance with the

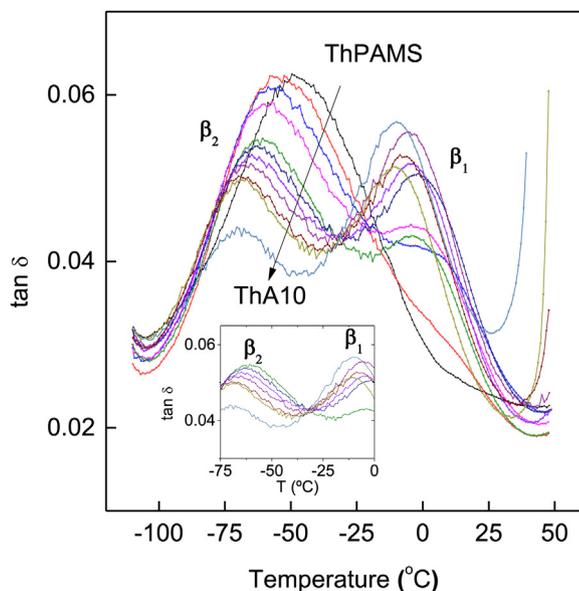


Fig. 6. Loss tangent at 1 Hz in the low temperature range for all specimens. Inset shows the isobestic point linking β_1 and β_2 for cured adducts ThA4 – ThA10.

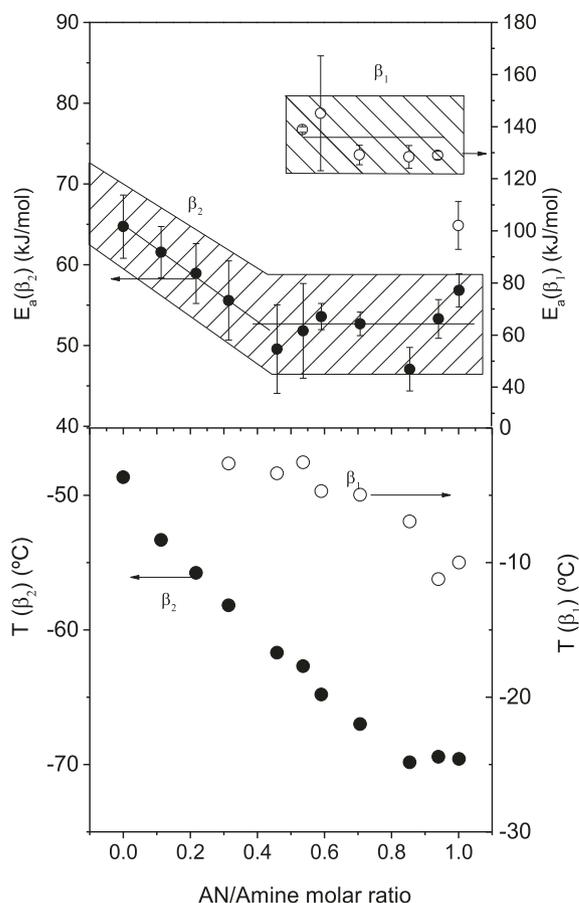


Fig. 7. Up: activation energies for the β_2 (left) and β_1 (right) relaxations as a function of the nitrile content. Error bars correspond to the fitting standard deviation. Lines and shadow areas are eye guides Bottom: peak temperatures for β_2 (left) and β_1 (right) relaxations.

two following facts: i) aza-Michael addition progressively lowers the amount of primary amine which lowers the amount of hydroxypropylether groups, and ii) amine functionalities stop being trifunctional crosslinks each time a nitrile is added to them, hence, crosslinking degree decreases.

Shifting of the β_2 transition to lower temperatures as crosslinking degree decreases has been already observed by Monnerie [25], among others [26], and should be followed by a reduction of the activation energy. This is observed in Fig. 7, where $E_a(\beta_2)$ is plotted as a function of nitrile molar ratio but only up to ~40% nitrile. At higher nitrile contents activation energy seems to reach a constant value.

Interestingly, Fig. 6 shows that as nitrile content increases, a new relaxation (β_1) appears shifted to higher temperatures, around 0 °C. At low nitrile contents this relaxation overlaps with β_2 being impossible to determine both the peak temperatures and the activation energies but, as shown in Fig. 7, at nitrile contents higher than ~50% peak temperatures seem to slightly decrease while $E_a(\beta_1)$ seems to be constant around the value of 139 kJ mol^{-1} . It should be noted also that at these high nitrile contents $E_a(\beta_2)$ also remains almost constant around the value of 52 kJ mol^{-1} .

The origin of this new relaxation is not straightforward. Since the intensity of this relaxation grows with nitrile content a parallelism with the β relaxation of polyacrylonitrile (PAN) seems to be plausible. However, this last relaxation appears at 330–340 K in PAN, its activation energy is around $110 \pm 10 \text{ kJ mol}^{-1}$ and involves 8 monomeric units [27].

Fortunately, detailed inspection of Fig. 6 reveals the presence of an isosbestic point at $-31\text{ }^{\circ}\text{C}$ linking β_2 and β_1 relaxations for thermosets ThA4 – ThA10. To the authors knowledge, isosbestic points in the mechanical relaxations of amorphous polymers are uncommon although they have been observed in the dielectric relaxations of partially crystalline polymers [28,29]. The presence of an isosbestic point suggests that the new β_1 relaxation grows at the expense of β_2 , i.e. as nitrile content increases the β_2 relaxation transforms into the β_1 . This is verified by the constancy of the sum of both loss tangents (not shown). In addition, since β_1 has a notably higher activation energy, the number of atoms involved in the relaxation must be also higher [27], hence, it should involve a more extended region probably comprising the hydroxypropylether group, the tertiary amine, the nitrile side chain and the propyl chain that connects the whole ensemble with the polyorganosiloxane cyclic or linear oligomers. This proposed region is illustrated in Scheme 2.

Why the isosbestic point is not observed for samples ThA1 – ThA3 may be associated to some degree of intermolecular cooperativity which gradually disappears as hydroxypropylether moiety becomes progressively isolated or diluted in the network, although it should not be discarded an effect of the characteristic heterogeneity of these samples.

3.2.2. High temperature relaxations, T_{α} and rubber modulus

In the high temperature range, networks present a single well defined relaxation associated to the α relaxation (Fig. 5a, b) except for the PAMS and ThA1 systems, where loss tangent is broad and probably reflects some kind of heterogeneity due to the initial poor miscibility of DGEBA with PAMS and with low nitrile adducts. It is known that DGEBA-PAMS system undergoes reactive compatibilization using a simple one step curing protocol at high curing temperatures; however, some network heterogeneities remain resulting in a broadening of the loss tangent [9], although other authors [7] obtained a single well defined peak using a different curing protocol. To verify if nitrile moieties help in compatibilizing the hardener with DGEBA, at least in the micron range, PAMS and the adducts were doped with 4-amino-1,8-naphthalic anhydride, a fluorescent label, and images of the curing systems were taken by laser scanning confocal microscopy in the postgel stage after curing at low temperatures ($50\text{ }^{\circ}\text{C}$). In Fig. 8 we present those images, where the bright regions correspond to PAMS or adduct rich domains. For networks with PAMS and adducts A1–A3, the observed morphology clearly reflects immiscibility of the components at low temperatures; however, as nitrile content increases, both

components progressively become more miscible, and for adducts A5 – A10, the networks appear completely miscible.

Therefore, it seems that there is a relationship between the miscibility of both components and the narrowing of the loss tangent peak for the α relaxation (see Table 1), which is commonly associated with the spatial distribution of crosslinking density [19,30]. A recent work on double epoxy networks also shows a broadening in $\tan\delta$ compared with unimodal networks [31].

Another interesting effect of the nitrile incorporation into the network is the increment of the loss tangent and, specifically for ThA10, the notably high value it achieves at temperatures near room temperature. Incorporation of flexible nitrile side chains do not contribute to the elasticity of the network but provide a frictional pathway for dissipating mechanical work. The high values of loss tangent are similar to those presented by the so-called super-damping elastomers, which range between 0.5 and 0.8.

Glass transition temperatures were determined from the α relaxation loss tangent peaks and Young's modulus in the rubbery state was obtained at $T_{\alpha} + 50\text{ K}$; both data appear in Table 1. Rubber moduli for DGEBA epoxy – aliphatic amine resins are usually found in the order of $\sim 50\text{ MPa}$ depending on crosslink density and network structure. This is the case of the early reported data on linear polyamines [32] (DETA, TETA, TEPA). The very high values found for the systems studied here have not been found in the literature; only tetrafunctional epoxies cured with anhydrides present exceedingly higher modulus values [33]. However, using branched aliphatic amine hardeners of functionality $f > 4$ or quasis dendrimers (for example, N,N,N',N',N''-penta(3-aminopropyl)-diethylenetriamine), a noticeable increase in modulus up to $\sim 70\text{ MPa}$, which cannot be related only to an increased crosslinking density, has been achieved [34,35]. The concentration of elastically active chains (EANC), ν , has been calculated from the rubbery modulus and is presented in Table 1.


As it is commonly found in epoxy thermosets reduction of crosslinking degree is accompanied by a decrease in T_{α} . Crosslinks reduce configurational entropy as well as the free volume and the frequently used models that account for these effects are those of DiMarzio [36], DM, and Fox–Loshaek [37], F-L.

The basic equations for F-L and DM models are given by Eqs. (1) and (2) respectively.

$$T_g = T_{g,l} + K_{FL}\nu \quad (1)$$

$$T_g = T_{g,l} / (1 - K_{DM}F \cdot \nu) \quad (2)$$

T_g is the glass transition temperature of a network having ν

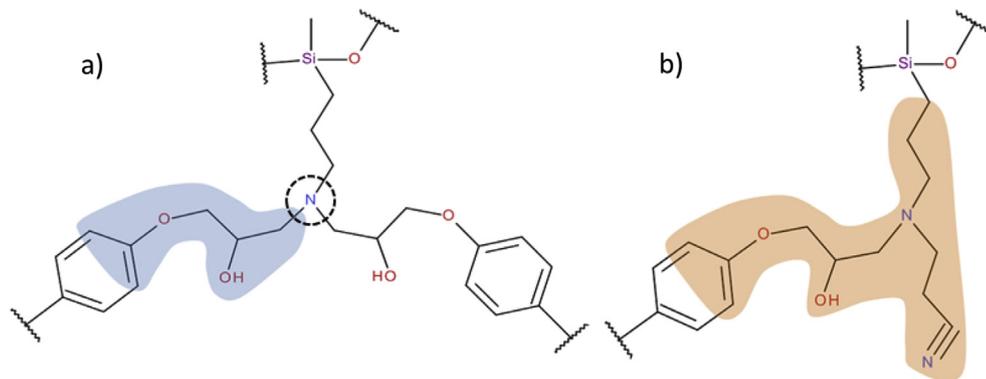

Scheme 2. a) Primary amines transform into tertiary amines which act as trifunctional crosslinks in DGEBA-PAMS cured networks. b) When a nitrile is added, the secondary amine reacts with an epoxy group but stops being a crosslink of the network. Shaded areas show the region involved in the β_2 relaxation (a), as reported in the literature, and the proposed region for the β_1 relaxation (b).

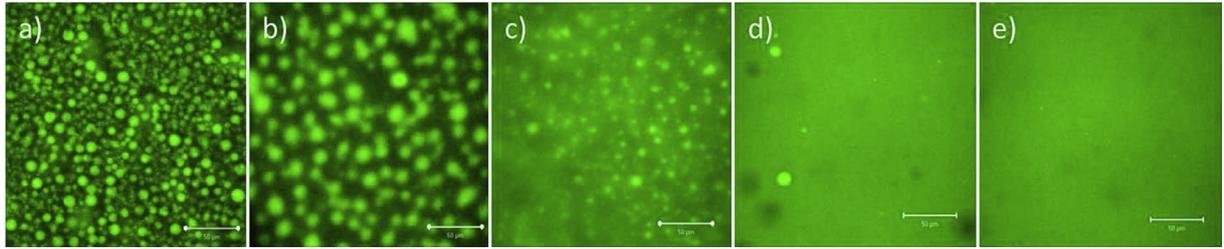


Fig. 8. Laser scanning confocal microscopy images of systems a) ThPAMS, b) ThA1, c) ThA3, d) ThA5 and e) ThA7. Scale bar is 50 microns.

elastically active chains (mol kg^{-1}); $T_{g,l}$ is the glass transition temperature of a linear polymer with the same composition as the network; F is the flex parameter (g mol^{-1}) that accounts for the chain stiffness; K_{FL} and K_{DM} are the F-L (in K g mol^{-1}) and DM constants respectively.

The use of these models requires the knowledge of the elastically active chain concentration (EANC) which can be obtained from a model of the network structure. In conventional thermosetting systems knowledge of this structure is straightforward assuming that tertiary amines are tri-functional crosslinks. In our hybrid systems, in addition to tertiary amines we have silicon atoms from the cyclics fraction, which may participate as trifunctional crosslinks, and the non-terminal silicon atoms from the linear fraction, which also may participate as trifunctional crosslinks (see Scheme 2). However, two of the three chains emerging from a silicon atom consist of a single oxygen atom and it appears to be quite unreasonable to consider them as elastic chains. Alternatively, polysiloxane chain and cyclic molecules can be considered as crosslinks as a whole, but EANC data derived from this model (not shown) are far from those obtained experimentally (Table 1). A paper dealing with this disagreement is under preparation but for the present discussion we have explored the use of ν calculated from elasticity measurements.

Fitting to F-L and DM models is presented in Fig. 9. Although current precision in the measurement of the relaxation temperature and Young's moduli do not allow to ascertain which model better reflects the behavior of our systems, the values of the fitting parameters are coincident with data for similar systems and have physical sense. For example $T_{g,l} = 312\text{--}319\text{ K}$ is a reasonable value for a linear analogue of the chains between crosslinks, and the flex parameter $F \sim 12\text{ g mol}^{-1}$ (assuming $K_{DM} \sim 2$ as it is commonly reported in the literature [19]) is very similar to data for fully aliphatic systems containing flexible bonds [38](—O—).

Table 1

Density, glass transition temperature, breadth of the relaxation, Young's modulus in the rubbery state and concentration of elastically active chains.

Sample	ρ^a kg m ⁻³ [3]	T_g °C	$\Delta \tan \delta^b$ °C	E^c MPa	ν^d mol kg ⁻¹
ThPAMS	1170	141.9	45.7	138	10.55
ThA1	1159	133.0	34.1	117	9.00
ThA2	1169	127.5	29.6	114	8.73
ThA3	1150	117.2	26.0	101	7.87
ThA4	1159	106.3	25.5	92	7.02
ThA5	1150	99.8	22.3	—	—
ThA6	1187	90.3	21.3	60	4.73
ThA7	1188	81.7	20.5	51	4.17
ThA8	1191	72.0	21.1	34	2.93
ThA9	1191	62.6	19.2	29	2.58
ThA10	1197	53.2	17.0	19	1.74

^a Measured at 35.1 °C.

^b Measured at half width.

^c Rubber modulus measured at $T_g + 50$ °C.

^d calculated from Young's moduli according to $\nu = E_{rub}/3RT\rho$.

Therefore, thermal relaxations are coherent with elastic behavior since the later helps to explain the former, but the question about the network model that supports the experimental concentration of elastically active chains needs a deeper thought.

4. Conclusions

A mixture of linear and cyclics of PAMS, well characterized by MALDI, was modified with acrylonitrile via aza-Michael addition yielding oligomers with controlled primary: secondary amine ratios and with an improved miscibility with DGEBA epoxy resin (for AN:NH₂ ratios higher than 0.4). Incorporation of nitrile groups induces positive deviations of T_g as the nitrile content increases, and fitting to Gordon Taylor, Kwei and Weiss equations revealed weak attractive interactions between pendant groups.

A broad range of organo-inorganic thermosets were prepared with AN:NH₂ ratios ranging between 0 and 1. The low temperature mechanical behavior shows a single relaxation for ThPAMS, β_2 , which was attributed to the hydroxypropylether moiety as it is commonly found in epoxy systems. However, as nitrile content was increased an additional relaxation appeared at higher temperatures, β_1 , with a higher activation energy. It was found that both relaxations were linked by an isosbestic point which was explained assuming that the molecular segment associated to β_1 was longer and included that for β_2 relaxation.

Modulus of elasticity at small deformations in the plateau regime was measured by DMTA giving very high values, even higher than any reported epoxy system cured with amines. Consequently, EANC derived from experiments were very high and no rational model based on compositional analysis could account for this disagreement. To explain the high T relaxations common

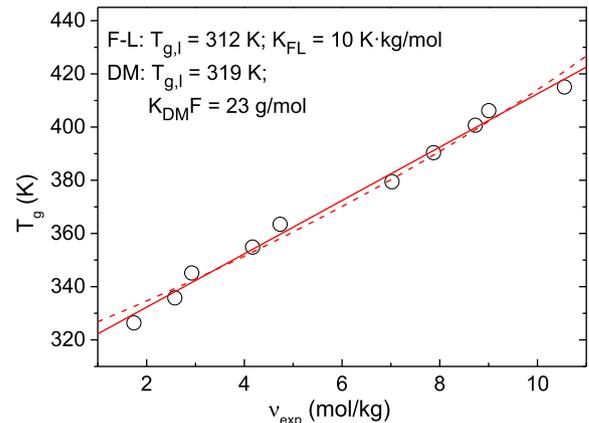


Fig. 9. Variation of the glass transition temperature as a function of the concentration of elastically active chains calculated from elasticity measurements. Continuous line corresponds to fitting to the Fox-Loshak equation; dashed line corresponds to the DiMarzio equation fit. Fitting parameters are indicated in the inset.

structure-T_g relationships were used along with the experimentally determined EANC from DMTA and reasonable fitting parameters were obtained.

Acknowledgment

Authors wish to thank Spanish Ministerio de Economía y Competitividad for funding this work under grant MAT2010-17091.

References

- J.J. Chruściel, E. Leśniak, Modification of epoxy resins with functional silanes, polysiloxanes, silsesquioxanes, silica and silicates, *Prog. Polym. Sci.* 41 (2015) 67–121.
- M. Srividhya, M.S. Lakshmy, B.S.R. Reddy, Chemistry of siloxane amide as a new curing agent for epoxy resins: material characterization and properties, *Macromol. Chem. Phys.* 206 (2005) 2501–2511.
- E. Yilgör, I. Yilgör, Silicone containing copolymers: synthesis, properties and applications, *Prog. Polym. Sci.* 39 (2014) 1165–1195.
- S.-S. Hou, Y.-P. Chung, C.-K. Chan, P.-L. Kuo, Function and performance of silicone copolymer. Part IV. Curing behavior and characterization of epoxy-siloxane copolymers blended with diglycidyl ether of bisphenol-A, *Polymer* 41 (2000) 3263–3272.
- J.C. Cabanelas, B. Serrano, J. Gonzalez-Benito, J. Bravo, J. Baselga, Morphology of epoxy/polyorganosiloxane reactive blends, *Macromol. Rapid Commun.* 22 (2001) 694–699.
- J.C. Cabanelas, B. Serrano, M.G. González, J. Baselga, Confocal microscopy study of phase morphology evolution in epoxy/polysiloxane thermosets, *Polymer* 46 (2005) 6633–6639.
- M. Gonzalez, P. Kadlec, P. Štěpánek, A. Strachota, L. Matějka, Crosslinking of epoxy-polysiloxane system by reactive blending, *Polymer* 45 (2004) 5533–5541.
- M. González, Termoestables híbridos basados en resinas epoxi hidrogenadas y polisiloxanos: curado, morfología y modificación con HTPB y PMMA, PhD Thesis, Universidad Carlos III, Madrid, 2008.
- J.C. Cabanelas, B. Serrano, J. Baselga, Development of co-continuous morphologies in initially heterogeneous thermosets blended with PMMA, *Macromolecules* 38 (2005) 961–970.
- J.C. Cabanelas, S.G. Prolongo, B. Serrano, J. Bravo, J. Baselga, Water absorption in polyaminosiloxane-epoxy thermosetting polymers, *J. Mat. Proc. Tech.* 143–144 (2003) 311–315.
- S.G. Prolongo, J.C. Cabanelas, J. Baselga, Reactive compatibilization of epoxy/polyorganosiloxane blends, *Macromol. Symp.* 198 (2003) 283–293.
- B.D. Mather, K. Viswanathan, K.M. Miller, T.E. Long, Michael addition reactions in macromolecular design for emerging technologies, *Prog. Polym. Sci.* 31 (2006) 487–531.
- J.C. Cabanelas, Polisiloxanos reactivos. Agentes de compatibilización y curado, PhD Thesis, Universidad Carlos III de Madrid, 2000.
- E. Dermitzaki, B. Wunderle, J. Bauer, H. Walter, B. Michel, Structure Property correlation of epoxy resins under the influence of moisture and comparison of diffusion coefficient with MD-simulations, in: Proceedings of the IEEE 9th. Int. Conf. on Thermal, Mechanical and Multiphysics Simulation and Experiments in Micro-Electronics and Micro-Systems, EuroSimE 2008, Freiburg-im-Breisgau, Germany, April 2008.
- M.B. Smith, *Methods of Non- α -amino Acid Synthesis*, second ed., CRC Press, Boca Raton, 2013, p. 65.
- C. Mukherjee, A.K. Misra, *Lett. Org. Chem.* 4 (2007) 54–59.
- M. González, J.C. Cabanelas, J. Baselga, in: T. Theophanides (Ed.), *Infrared Spectroscopy – Materials Science, Engineering and Technology*, In-Tech, 2012. Chap. 13.
- D. Wang, Y. Liu, Z. Hu, C. Hong, C. Pan, Michael addition polymerizations of trifunctional amines with diacrylamides, *Polymer* 46 (2005) 3507–3514.
- J.P. Pascault, H. Sautereau, J. Verdu, R.J.J. Williams, *Thermosetting Polymers*, Marcel Dekker Inc., New York, 2002, p. p 85.
- H.A. Schneider, J. Rieger, E. Penzel, The glass transition temperature of random copolymers: 1. Experimental data and the Gordon-Taylor equation, *Polymer* 38 (1997) 325–337.
- M. Aubin, R.E. Prud'homme, Analysis of the glass transition temperature of miscible polymer blends, *Macromolecules* 21 (1988) 2945–2949.
- T.K. Kwei, The effect of hydrogen bonding on the glass transition temperatures of polymer mixtures, *J. Polym. Sci. Polym. Lett.* 22 (1984) 307–313.
- X. Lu, R.A. Weiss, Relationship between the glass transition temperature and the interaction parameter of miscible binary polymer blends, *Macromolecules* 25 (1992) 3242–3246.
- P.R. Couchman, Compositional variation of glass-transition temperatures. 2. application of the thermodynamic theory to compatible polymer blends, *Macromolecules* 11 (1978) 1156–1161.
- L. Heux, J.L. Halary, F. Lauprêtre, L. Monnerie, Dynamic mechanical and 13C n.m.r. investigations of molecular motions involved in the β relaxation of epoxy networks based on DGEBA and aliphatic amines, *Polymer* 38 (1997) 1767–1778.
- J.-F. Shi, P.T. Inglefield, A.A. Jones, M.D. Meadows, Sub-glass transition motions in linear and cross-linked bisphenol-type epoxy resins by deuterium line shape NMR, *Macromolecules* 29 (1996) 605–609.
- a) V.A. Bershtein, V.M. Egorov, *Differential Scanning Calorimetry of Polymers*, Ellis Horwood, Chichester, 1994, p. 20;
b) V.A. Bershtein, V.A. Ryzhov, *Adv. Polym. Sci.* 114 (1994) 93–121.
- F. Kremer, A. Schonhals, *Broadband Dielectric Spectroscopy*, Springer, Berlin, 2003.
- S. Cerveny, P. Zinck, M. Terrier, S. Arrese-Igor, A. Alegria, J. Colmenero, Dynamics of amorphous and semicrystalline 1,4-trans-poly(isoprene) by dielectric spectroscopy, *Macromolecules* 41 (2008) 8669–8676.
- A.T. Detwiler, A.J. Lesser, Characterization of double network epoxies with tunable compositions, *J. Mater. Sci.* 47 (2012) 3493–3503.
- I.M. McAninch, G.R. Palmese, J.L. Lenhart, J.J. La Scala, Characterization of epoxies cured with bimodal blends of polyether amines, *J. Appl. Polym. Sci.* 130 (2013) 1621–1631.
- D. Katz, A.V. Tobolsky, Rubber elasticity in a highly crosslinked epoxy system, *Polymer* 4 (1963) 417–421.
- P. Guerrero, K. De la Caba, A. Valea, M.A. Corcuera, I. Mondragon, Influence of cure schedule and stoichiometry on the dynamic mechanical behaviour of tetrafunctional epoxy resins cured with anhydrides, *Polymer* 37 (1996) 2195–2200.
- J. Wan, Z.-Y. Bu, C.-J. Xu, B.-G. Li, H. Fan, Preparation, curing kinetics, and properties of a novel low-volatile starlike aliphatic-polyamine curing agent for epoxy resins, *Chem. Eng. J.* 171 (2011) 357–367.
- J. Wan, C. Li, Z.-Y. Bu, C.-J. Xu, B.-G. Li, H. Fan, A comparative study of epoxy resin cured with linear diamine and a branched polyamine, *Thermochim. Acta* 188 (2012) 160–172.
- E.A. DiMarzio, On the second-order transition of a rubber, *J. Res. NBS* 68A (1964) 611–617.
- T.G. Fox, S. Loshaek, Influence of molecular weight and degree of crosslinking on the specific volume and glass temperature of polymers, *J. Polym. Sci.* 15 (1955) 371–390.
- V. Bellenger, J. Verdu, E. Morel, J. Polym, Effect of structure on glass transition temperature of amine crosslinked epoxies, *Sci. B Polym. Phys.* 25 (1987) 1219–1234.